

PHENOTYPIC CORRELATIONS BETWEEN JUVENILE-MATURE WOOD DENSITY AND GROWTH IN BLACK SPRUCE

*Ahmed Koubaa*¹

Post-Doctoral Research Fellow

S. Y. Zhang[†]

Research Scientist and Group Leader
Resource Assessment and Utilization Group
Forintek Canada Corp.
Sainte-Foy, Québec, Canada G1P 4R4

Nathalie Isabel

Research Scientist

Jean Beaulieu

Research Scientist
Natural Resources Canada
Canadian Forest Service-Quebec Region
1055 du PEPS, P.O. Box 3800
Sainte-Foy, Québec, Canada G1V 4C7

and

Jean Bousquet

Professor and Director
Centre de Recherche en Biologie Forestière
Université Laval
Sainte-Foy, Québec, Canada G1K 7P4

(Received March 1999)

ABSTRACT

Phenotypic correlations between juvenile-mature wood density and growth were examined based on increment core samples from two plantations, a provenance test and a commercial plantation, of black spruce [*Picea mariana* (Mill.) B.S.P.]. The ring density components are significantly correlated to their respective ring width components: earlywood and ring densities are negatively correlated to ring and earlywood widths, respectively, while ring and latewood densities are positively correlated to latewood width. These hold true in both juvenile and mature wood. However, the correlation between ring width and ring density decreases with increasing age. This suggests that the correlation between wood density and growth rate tends to lessen as the tree ages. For each character, the correlation between juvenile and mature wood is significant but moderate. Thus, juvenile wood characters are only indicative of mature wood ones. On the other hand, trees with 12 growth rings from the pith were good predictors of wood density and radial growth of the whole tree. Individual growth rings from the juvenile-mature wood transition zone can be used to predict to some extent the wood density of either mature wood or the whole tree.

Keywords: Black spruce, juvenile wood, mature wood, ring density, ring width.

¹ This research was conducted while the first author was employed by the Centre de Recherche en Biologie Forestière, Université Laval and Forintek Canada Corp.

[†] Member of SWST.

INTRODUCTION AND BACKGROUND

With the evolution in forest management toward shorter rotations and the use of genetically improved planting stocks for growth and volume, wood quality has become a major concern in the forest products industry (Bendtsen 1978; Kellogg 1989; Vargas-Hernandez and Adams 1992; Zhang 1994; Zhang et al. 1996). Faced with this trend, tree breeders have realized that wood quantity and quality cannot be treated as independent factors and that wood quality traits should be incorporated into any tree breeding programs where wood is to be the end product (Keith and Kellogg 1986; Zobel and van Buijtenen 1989; Magnussen and Keith 1990). To implement this strategy and obtain optimal gains, it is essential to study the relationship between growth traits and wood density and other quality traits.

The relationship between growth rate and wood density has been studied intensively, but is rather controversial. Hence, some researchers have reported that in conifers, there is little relationship between ring width and wood density (Zobel and van Buijtenen 1989; Zobel and Jett 1995). However, others have stated that accelerated growth reduces wood density, especially in conifers other than hard pines (Zobel and van Buijtenen 1989). For spruces, many studies (Keith 1961; Olesen 1976; Beaulieu and Corriveau 1985; Corriveau et al. 1987, 1990, 1991; Rozenberg and Cahalan 1997) have also reported negative relationships between growth rate and wood density. In black spruce, the relationship is still contradictory. On one hand, Risi and Zeller (1960) showed that ring width and wood density of mature trees were not correlated. In Newfoundland mature stands, the relationship between growth rate and wood density was weak and dependent on location and environmental factors (Hall 1984). On the other hand, Boyle et al. (1987) found a negative correlation of wood density with both the tree height and the tree diameter in 15-yr-old trees. In addition, Zhang et al. (1996) reported that wood density

was negatively related to growth rate in juvenile wood for a 15-yr-old plantation. Zhang (1995) recently examined the relationship of growth rate to wood density and mechanical properties in 16 mature tree species belonging to 4 distinct wood categories and reported negative correlations for softwoods. For plantation-grown white spruce, mature trees with high ring width led to low density, high juvenile wood content, and low strength properties, while trees with high ring density and moderate or slow growth rate led to satisfactory strength properties (Zhou and Smith 1991). From these results, relationship of growth rate to wood density in black spruce seems to be age-dependent. The negative relationship is statistically significant in young trees (Boyle et al. 1987; Zhang et al. 1996) but not significant in mature trees (Risi and Zeller 1960; Hall 1984). However, there is no information available on the evolution of this relationship with tree age.

Breeding programs usually take many years to complete every cycle. As a result, a selection at an early age would reduce the length of breeding cycle and be cost-effective. In fact, the age of selection, to a large extent, determines the length of breeding cycle and the amount of genetic gain that can be achieved per unit of time (Lambeth 1980; McKeand 1988). To pursue selection at an early age, it is important to understand the relationships between juvenile and mature wood at both genetic and phenotypic levels. Determining the extent of any relationship between juvenile and mature wood properties and between juvenile wood and values for the whole tree is of great interest and utility for breeding purposes (Zobel and Sprague 1998). In white spruce, Corriveau et al. (1987) reported moderately positive correlations (both phenotypic and genetic) between juvenile density and mature wood density. Since genetic correlations were of the same order and sign as the phenotypic correlations, they concluded that mass selection could be made at a younger age for genetic improvement of wood density or wood mass production in the species. In Norway

spruce, Nepveu and Birot (1979) reported high simple and canonical correlations of juvenile wood density and growth with mature wood density and growth. Blouin et al. (1994) reported that mature and juvenile wood densities were highly correlated in the same species. The available information on the juvenile-mature wood relationships in pines was summarized by Zobel and Sprague (1998).

The juvenile-mature wood relationships are important not only for tree breeding purposes but also for end-use purposes. For the end users, the relationships between juvenile wood properties and those of whole trees are even more important than juvenile-mature wood relationships. Such relationships are needed for an early assessment of wood available at harvest time (Zobel and Sprague 1998).

This study was initiated to examine the phenotypic relationships between juvenile and mature wood characteristics in black spruce [*Picea mariana* (Mill.) B.S.P.], the most important commercial species in eastern Canada. Specifically, the objectives of this study were to: 1) examine the extent of phenotypic correlations among some intra-ring characteristics within and between juvenile and mature wood zones; 2) determine the age upon which mature wood density and growth rate could be predicted; and 3) evaluate the possibility of predicting total wood density from individual rings. Since there was no family structure for the plantations sampled, this study examined only phenotypic correlations.

MATERIALS AND METHODS

A provenance test was established in 1974 using a randomized complete 6-block design with 16-tree (4×4) square plots on 6 different sites distributed throughout the province of Quebec. Each square plot had trees spaced at $2.5 \text{ m} \times 3 \text{ m}$ (Beaulieu et al. 1989). At the end of the 1995 growing season, 86 provenances and 12 trees per provenance from 3 blocks were sampled in the test site located at Mont-Laurier (lat. $46^{\circ}36'N$, long. $75^{\circ}48'W$, alt. 300 m). In this location, the average an-

nual precipitation is 910 mm and the average annual temperature is $3.5^{\circ}C$. The length of the growing season varies from 170 to 180 days. The soil is deep alluvial sand. Moreover, at the end of the 1996 growing season, 944 trees were sampled from a 50-yr-old black spruce commercial plantation in Victoriaville (lat. $46^{\circ}01'N$, long. $72^{\circ}33'W$, alt. 90 m). The initial spacing for the plantation was $2 \text{ m} \times 2 \text{ m}$. The average annual precipitation in Victoriaville is 1,000 mm, and the average annual temperature is $4.5^{\circ}C$. The length of the growing season varies from 180 to 190 days.

From a constant compass direction, an increment core (6 mm in diameter) was taken at breast height from each tree selected in both plantations. All increment cores were wrapped in plastic bags and kept frozen until the sample preparation. The core samples were sawn to a 1.57-mm thickness longitudinally. The strips were then extracted with cyclohexane/ethanol solution 2:1 (v/v) for 24 h and with distilled water for another 24 h. X-ray densitometry was used to measure wood density. After conditioning, rings from the pith to the bark were scanned in the air-dry condition. Data on earlywood density (EWD), latewood density (LWD), and ring density (RD) of individual rings were obtained based on the intra-ring microdensitometric profiles. The same profiles served for determining earlywood width (EWW), latewood width (LWW), and ring width (RW) of individual rings. The boundaries delimiting earlywood and latewood (540 kg/m^3) and between the end of the latewood zone of a ring and the beginning of the earlywood of the following ring (450 kg/m^3) were determined experimentally by undertaking preliminary analyses of some ring density profiles of a subsample of cores. During the scanning, precautions were taken to eliminate incomplete or false rings, and rings with compression wood or branch tracers. The averages for each parameter were weighted on the basis of ring area. The latewood percentage (LWP) was calculated as the ratio of latewood width to ring width.

The normality of the experimental data was

TABLE 1. Descriptive statistics for the Mont-Laurier provenance test and the Victoriaville commercial plantation.

Plantation	RD (kg/m ³)	EWD (kg/m ³)	LWD (kg/m ³)	RW (mm)	EWL (mm)	LWL (mm)	LWP (%)
Mont-Laurier†							
Average‡	443	396	609	3.36	2.6	0.76	23.1
SD	37	2.7	24	0.63	0.63	0.26	7.9
CV (%)	8.4	6.8	4	18.7	24.2	34.2	34.2
Victoriaville†							
Average‡	441	375	623	2.51	1.9	0.60	27
SD	30	20	25	0.43	0.42	0.13	6.3
CV (%)	6.8	5.3	4	17.1	22.1	21.7	23.3
Victoriaville							
Average‡	440	382	625	3.34	2.59	0.75	23.9
SD	30	19	25	0.58	0.59	0.19	6.2
CV (%)	6.8	5	4	17.4	22.3	25.3	25.9

Abbreviations: RD, ring density; EWD, earlywood density; LWD, latewood density; RW, ring width; EWL, earlywood width; LWL, latewood width; LWP, latewood proportion; SD, standard deviation; CV, coefficient of variation.

† Whole disc average.

‡ Averages are weighted on ring area.

|| Averages of the first 15 rings.

verified using the Wilk-Shapiro test (SAS 1988a). Correlation and regression analyses were conducted on the data using CORR and REG SAS procedures (SAS 1988b). Because of the large sample size, a conservative significance level ($\alpha = 0.01$) was set *a priori* for declaring results significant. Furthermore, a Bonferroni correction was applied to the significance level for taking account of the numerous simultaneous tests (Neter et al. 1985). Another set of analyses based on tree means was conducted to see how well average mature wood density (MWD) could be predicted from juvenile wood characters using stepwise regression analysis (SAS 1988b). The significant level for entry and staying in the model for any juvenile wood property was specified as $\alpha = 0.01$.

RESULTS AND DISCUSSION

The average wood density for the provenance test (443 kg/m³) was similar to that of the commercial plantation (441 kg/m³) despite differences in age (Table 1). Trees grown in these plantations had higher average wood density than that reported by Zhang and Morgenstern (1996) for a black spruce family test in New Brunswick (399 kg/m³). As shown in Table 1, earlywood density for the provenance

test was higher than that of the commercial plantation while the latewood density was lower. Even when both plantations were compared at the same age,² the weighted averages for earlywood and latewood densities were still statistically different ($P < 0.01$). The average ring, earlywood, and latewood widths for the provenance test were higher than those of the commercial plantation (Table 1). This is likely due to the age differences between both plantations: at the same age, the ring, earlywood, and latewood widths of both plantations were comparable.

Correlation among traits

For both plantations, ring density was positively correlated with earlywood and latewood densities (Table 2) and in both cases, the correlation between ring density and earlywood density was higher than between ring density and latewood density. Trees from the Victoriaville plantation with high earlywood density showed a tendency to exhibit high latewood density in the juvenile wood, whereas this relationship was not observed in mature wood (Table 3). On the other hand, ring den-

² Means for the trees in the Victoriaville plantation were computed for the first 15 annual rings.

TABLE 2. Correlation coefficients between all possible pairs of intra-ring traits for the two plantations. Upper part, Victoriaville commercial plantation; lower part, Mont-Laurier provenance test.

	RD	EWD	LWD	RW	EWV	LWW	LWP
Ring density (RD)		0.87**	0.58**	-0.29**	-0.59**	0.73**	0.93**
Earlywood density (EWD)	0.91**		0.28**	-0.18**	-0.46**	0.67**	0.68**
Latewood density (LWD)	0.54**	0.43**		-0.24**	-0.39**	0.37**	0.50**
Ring width (RW)	-0.44**	-0.27**	-0.42**		0.95**	0.14**	-0.53**
Earlywood width (EWW)	-0.66**	-0.43**	-0.37**	0.91**		-0.18**	-0.75**
Latewood width (LWW)	0.69**	0.51**	0.43**	0.19**	-0.21**		0.71**
Latewood proportion (LWP)	0.88**	0.77**	0.48**	-0.35**	-0.68**	0.83**	

** Significant at $\alpha = 0.01$ after a Bonferroni correction. Hence, a P -value must be lower than or equal to $0.01/21 = 0.00048$ to be declared significant.

sity was strongly correlated with latewood proportion in both juvenile and mature wood (Table 3). Thus, latewood proportion and earlywood density seem more important in determining overall wood density than latewood density. As shown in Fig. 1, the correlation between ring density and latewood proportion was almost constant (about 0.83) over the tree age. However, the correlation between ring density and earlywood density decreased consistently with age. Thus, latewood proportion seemed more important than earlywood density in determining mature wood density.

This study also disclosed a negative relationship between growth rate and wood density in black spruce at the phenotypic level (Tables 2 and 3). Indeed, the correlation between ring density and ring width was negative and statistically significant. Earlywood density was also negatively correlated with both ring width and earlywood width. But it was different for latewood, as the correlation between latewood density and latewood width is positive. These observations were in agree-

ment with previous results (Zhang et al. 1996; Zhang 1998). Selection for high latewood width might have a positive effect on both wood density and tree growth because latewood width is positively correlated with ring density and ring width. These relationships remain to be confirmed at the genetic level. However, both genetic and phenotypic correlations between wood density and growth in black spruce were reported to be of the same order and sign in another study carried out on different sites (Zhang et al. 1996; Zhang and Morgenstern 1996).

The correlations of ring density with both ring and earlywood widths were weaker in mature wood (Table 3). This suggests that the negative effect of high radial growth on wood density decreases when the wood reaches maturity. The negative correlation was no longer statistically significant after 25 years of age (Fig. 2). These results were similar to those reported by Keith (1961), where a reduction in the correlation between growth rate and

TABLE 3. Correlation coefficients between the different traits for the juvenile (upper) and mature (lower) wood in the Victoriaville commercial plantation.

	RD	EWD	LWD	RW	EWV	LWW	LWP
Ring density (RD)		0.86**	0.59**	-0.33**	-0.53**	0.44**	0.91**
Earlywood density (EWD)	0.78**		0.31**	-0.31**	-0.42**	0.25**	0.61**
Latewood density (LWD)	0.47**	-0.01 n.s.		0.15**	0.02 n.s.	0.40**	0.50**
Ring width (RW)	-0.44**	-0.26**	-0.29**		0.95**	0.13**	-0.49**
Earlywood width (EWW)	-0.67**	-0.42**	-0.41**	0.96**		-0.20**	-0.74**
Latewood width (LWW)	0.71**	0.50**	0.39**	0.55**	0.32**		0.77**
Latewood proportion (LWP)	0.86**	0.65**	0.21**	-0.52**	-0.69**	0.34**	

** Significant at $\alpha = 0.01$ after a Bonferroni correction. Hence, a P -value must be lower than or equal to $0.01/21 = 0.00048$ to be declared significant.
n.s. = not significant.

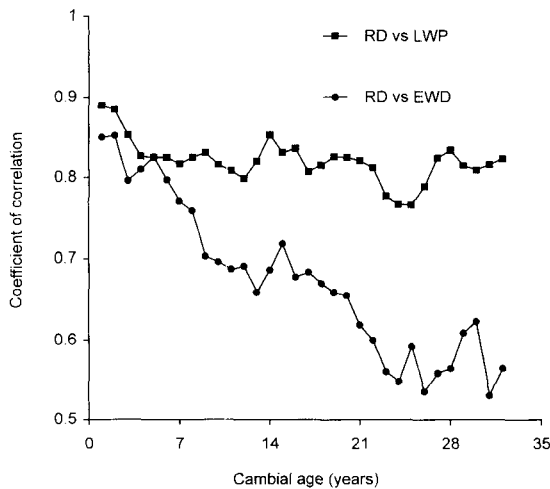


FIG. 1. Correlation of ring wood density (RD) with latewood proportion (LWP) and earlywood density (EWD) over tree age in the Victoriaville plantation.

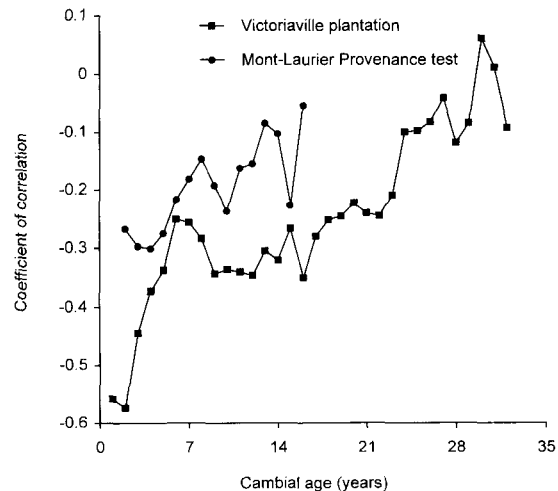


FIG. 2. Correlation between ring density with ring width over tree age in the Victoriaville plantation and Mont-Laurier provenance test.

wood density in mature wood of white spruce [*Picea glauca* (Moench.) Voss] was observed.

The negative relationship between ring width and ring density, although significant, was only moderate (Tables 2 and 3). Thus, it seems possible to identify some provenances or individuals that not only grow fast but also maintain high wood density, as was previously reported for white spruce by Corriveau et al. (1990). For example, at the Mont-Laurier site, provenance 323 was among the provenances that showed the highest growth rates (Beaulieu et al. 1989). This provenance still grew rapidly and its density (458 kg/m^3) was well above the average of all provenances (443 kg/m^3). Thus, it could be recommended for both fast growth and high wood density. On the other hand, provenance 437 was among the slow-growing provenances (Beaulieu et al. 1989). Its density (410 kg/m^3) was also below the average of all provenances. Consequently, this provenance could be not recommended for either fast growth or high wood density.

The effect of growth rate on wood density has also been studied within provenances (Table 4). A negative correlation between ring width and growth rate was observed for most provenances. A positive correlation, however,

was recorded for some provenances. These results suggest that it would be possible to identify some individuals within provenances that not only grow fast but also maintain high wood density, as was previously reported for white spruce (Corriveau et al. 1990).

Juvenile-mature wood relationships

Juvenile-mature wood correlations were studied for all measured traits (Table 5). Correlations between juvenile (rings 1–12) and mature wood (rings 18–30) traits were significant ($P < 0.01$) but moderate. Thus, the values of juvenile wood for these traits seem to be only indicative of those of mature wood. The highest correlation coefficients between mature and juvenile traits were found for ring density, earlywood density, and latewood proportion. This suggests that trees producing high wood density or latewood proportion during the juvenile phase continue to do so during the mature wood period. For each trait, the juvenile wood values explained from 30% to 46% of the variances in mature wood values. These results were concordant with previous reports on Douglas-fir (*Pseudotsuga menziesii* (Mirb.) Franco) (Abdel-Gadir et al. 1993; Keller and Thoby 1977), Norway spruce (*Picea*

TABLE 4. Correlation coefficients (r) between average ring density and total ring width based on tree averages in each provenance of the Mont-Laurier site.

Provenance	r	Provenance	r	Provenance	r
1539	-0.91 (0.00)	338	-0.44 (0.09)	4344	-0.10 (0.79)
6927	-0.85 (0.01)	4352	-0.42 (0.30)	437	-0.10 (0.77)
6902	-0.82 (0.02)	6909	-0.41 (0.30)	322	-0.09 (0.78)
353	-0.81 (0.00)	1531	-0.41 (0.18)	6903	-0.09 (0.79)
361	-0.81 (0.00)	360	-0.41 (0.21)	311	-0.08 (0.86)
6914	-0.79 (0.01)	3267	-0.40 (0.26)	4277	-0.04 (0.96)
6922	-0.74 (0.01)	329	-0.38 (0.28)	1329	-0.02 (0.95)
346	-0.73 (0.01)	359	-0.37 (0.30)	321	0.00 (0.99)
6930	-0.73 (0.04)	345	-0.37 (0.27)	315	0.01 (0.97)
335	-0.72 (0.02)	6938	-0.36 (0.38)	6804	0.03 (0.95)
6803	-0.71 (0.08)	331	-0.36 (0.28)	6917	0.04 (0.91)
6802	-0.70 (0.02)	6973	-0.35 (0.36)	340	0.06 (0.84)
368	-0.63 (0.05)	4360	-0.34 (0.37)	337	0.08 (0.84)
357	-0.58 (0.06)	6805	-0.33 (0.52)	348	0.08 (0.83)
355	-0.58 (0.08)	1528	-0.31 (0.35)	341	0.09 (0.79)
6901	-0.58 (0.06)	316	-0.30 (0.37)	363	0.10 (0.79)
344	-0.57 (0.08)	356	-0.30 (0.41)	6965	0.17 (0.65)
3293	-0.57 (0.11)	1529	-0.29 (0.38)	6968	0.21 (0.57)
326	-0.54 (0.07)	4351	-0.28 (0.50)	442	0.22 (0.61)
342	-0.54 (0.09)	6907	-0.25 (0.46)	352	0.25 (0.46)
1534	-0.53 (0.14)	4349	-0.24 (0.50)	367	0.27 (0.48)
349	-0.53 (0.09)	6801	-0.23 (0.55)	6967	0.31 (0.38)
369	-0.52 (0.10)	325	-0.23 (0.50)	6979	0.31 (0.46)
3268	-0.49 (0.21)	1628	-0.23 (0.48)	372	0.32 (0.32)
370	-0.48 (0.11)	330	-0.22 (0.58)	332	0.37 (0.30)
347	-0.48 (0.23)	328	-0.19 (0.59)	323	0.60 (0.05)
1538	-0.47 (0.24)	4353	-0.17 (0.71)	1530	0.69 (0.05)
4354	-0.44 (0.17)	333	-0.17 (0.67)	4355	0.85 (0.01)
336	-0.44 (0.10)	1847	-0.12 (0.76)	—	—

Values in parentheses are P -values for the hypothesis tests that the correlation coefficient = 0.

abies (L.) Karst.) (Nepveu and Birot 1979; Blouin et al. 1994), and white spruce (Corribeau et al. 1987).

The results of the stepwise regression analysis showed that only juvenile ring density

(JRD), juvenile earlywood width (JEW), and juvenile latewood width (JLWW) were significant in predicting mature wood density (MWD). The best fitted response function was (Eq. 1):

TABLE 5. Correlations among possible pairs of intra-ring characteristics between juvenile (rings 1–12) and mature (rings 18–30) wood in the Victoriaville plantation.

Juvenile wood	Mature wood						
	RD	EWD	LWD	RW	EW	LW	LWP
Ring density (RD)	0.68**	0.53**	0.36**	-0.21**	-0.36**	0.34**	0.60**
Earlywood density (EWD)	0.64**	0.62**	0.25**	-0.15**	-0.27**	0.33**	0.50**
Latewood density (LWD)	0.42**	0.18**	0.49**	-0.14**	-0.23**	0.18**	0.32**
Ring width (RW)	-0.26**	-0.19**	-0.02 n.s.	0.39**	0.41**	0.13**	-0.32**
Earlywood width (EW)	-0.40**	-0.28**	-0.13**	0.37**	0.44**	-0.01 n.s.	-0.44**
Latewood width (LW)	0.44**	0.26**	0.34**	0.04 n.s.	0.09 n.s.	0.44**	0.37**
Latewood proportion (LWP)	0.56**	0.37**	0.30**	-0.21**	-0.34**	0.30**	0.55**

** Significant at $\alpha = 0.01$ after a Bonferroni correction. Hence, a P -value must be lower than or equal to $0.01/49 = 0.0002$ to be declared significant.
n.s. = not significant to 99% probability level.

$$\begin{aligned} \text{MWD} = & (-68 \pm 28) + (1.17 \pm 0.06)\text{JRD} \\ & + (11 \pm 2)\text{JEW} \\ & - (35 \pm 15)\text{JLWW} \end{aligned} \quad (1)$$

Latewood proportion, ring width, and earlywood density were excluded from the model because they were highly correlated with the entering variables. From Mallows' Cp statistic ($C_p = 3.48$), the multiple regression model found had a small mean squares error with no indication of bias in the model (Neter et al. 1985). This analysis showed that juvenile ring density, earlywood width, and latewood width explained 49% of the variation in mature wood density. Although this result confirmed some potential value of juvenile wood characters in predicting the phenotypic value of mature wood density in black spruce, more than 50% of mature wood density was still not explained. Thus, care should be taken in predicting mature wood density from juvenile traits, especially for further genetic selection. In order to make an early selection, the use of other alternative methods such as marker-aided selection based on DNA markers should be investigated (Strauss et al. 1992).

Minimum age to predict wood density and radial growth

While the correlations between juvenile and mature wood traits were moderate and highly significant, it is most important to determine the earliest age at which the mature wood traits could be predicted satisfactorily. For example, selection for wood density would be efficient from 7 yr of age in coastal Douglas-fir (Vargas-Hernandez and Adams 1992). In Norway spruce, Nepveu and Birot (1979) showed that annual rings 5 to 12 could be used to predict mature wood density. In the present study, we examined the relationship between the tree average density at different ages from 3 to 30 and the whole tree average (Fig. 3). The linear relationship was weak at early ages. This indicates that wood density of very young trees is not a reliable predictor for wood density at later ages. However, the correlation

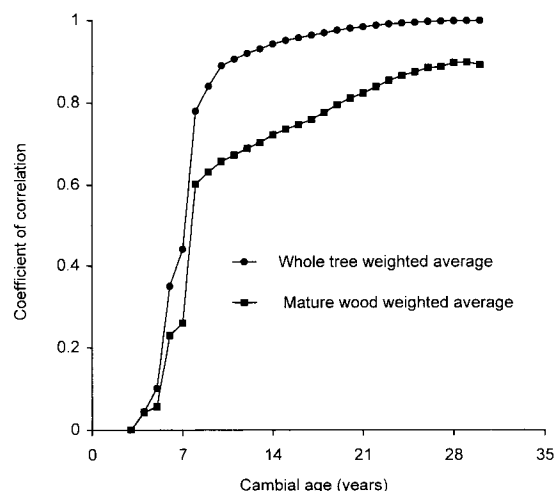


FIG. 3. Correlation of weighted average ring density at different ages with weighted average densities of the whole tree and mature wood in the Victoriaville plantation.

increased with tree age, then leveled off beyond the twelfth annual ring. This suggests that wood density of whole trees in black spruce would be satisfactorily predicted only from at least the first 12 annual rings at breast height. The same pattern of variation was found for the tree average ring width at different ages from 3 to 30 and the whole tree ring width average (Fig. 4). The correlation

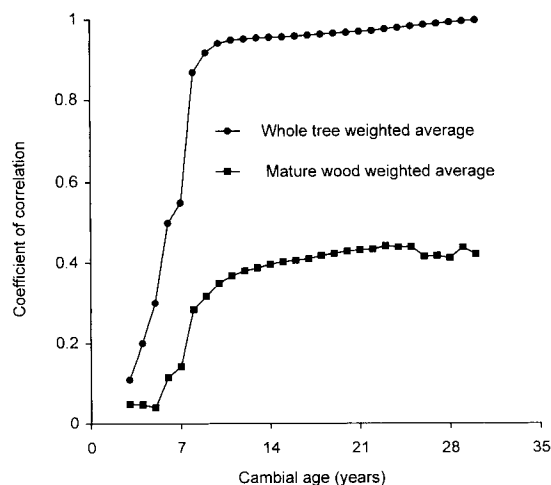


FIG. 4. Correlation of weighted average ring width at different ages with weighted ring widths of the whole tree and mature wood in the Victoriaville plantation.

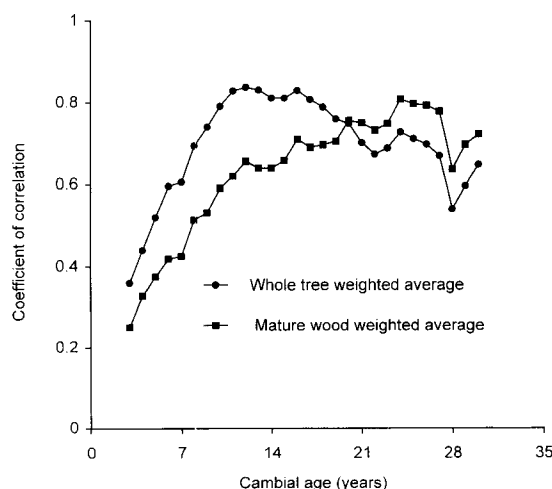


FIG. 5. Correlation of individual annual ring densities and densities of the whole tree and the mature wood in the Victoriaville plantation.

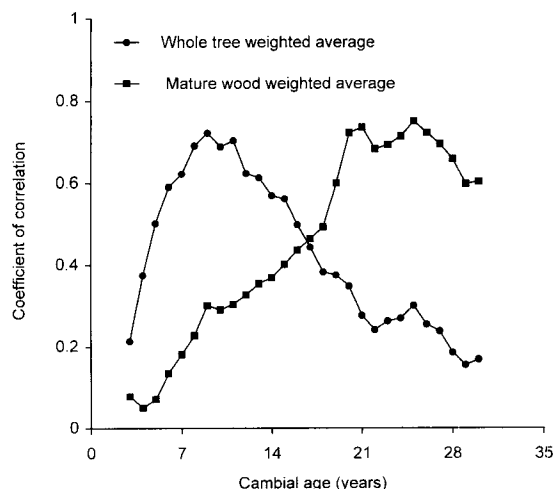


FIG. 6. Correlation between individual annual ring widths and ring widths of the mature wood and the whole tree in the Victoriaville plantation.

increased with age to reach a plateau beyond the tenth annual ring. Accordingly, at least 10 annual rings at breast height are needed to obtain a reliable prediction of the average growth rate in older trees. These results have some practical implications for both wood users and tree breeders. For wood users, they show that density and growth of the future wood supply could be assessed at a young age. If the genetic correlations for wood density and growth are in the same order and sign with phenotypic correlations, these results could significantly shorten a breeding cycle. However, for slow-growing trees such as black spruce, it takes almost 20 yr to reach 12 annual rings at breast height. This is still a long cycle, and other rapid alternatives to assess wood density and growth at early ages should be investigated.

Similar trends were found for the linear relationships between tree density and ring width at different ages (from 3 to 30) and the mature wood density (Fig. 3) and ring width (Fig. 4). Ages at which the leveling off started for mature wood weighted density (12 yr) and ring width (10 yr) were the same as that for the whole tree weighted averages. However, the correlations were lower for weighted mature wood averages. This was especially true

for ring width where the coefficient of correlation had dropped drastically (Fig. 4). This is likely due to the large physiological and environmental influence on black spruce growth, especially in juvenile wood (Panshin and de Zeeuw 1980; Zobel and van Buijtenen 1989; Zobel and Jett 1995; Zobel and Sprague 1998). The correlation coefficients for mature wood density were lower than those for whole trees (Fig. 2). In trees having 12 annual rings at breast height, the juvenile wood density explained only 46% (R^2) of the phenotypic variation of mature wood density (Table 5). These results are especially important for black spruce breeders since they show that early selection for mature wood density and growth may not pay off.

Prediction of density and growth performance from individual annual rings

Wood density (Fig. 5) and ring width (Fig. 6) of early annual rings were not closely correlated to those of either the mature wood or the whole tree. Thus, the use of these characters at early ages for prediction or selection purposes would be misleading and should be avoided. In contrast, the whole tree density and ring width were closely correlated with those

of growth rings from the juvenile-mature wood transition zone (Koubaa et al. 1999). Accordingly, the density and ring width of the whole tree could be predicted with a fair degree of confidence from individual annual rings if these annual rings were taken from the juvenile-mature wood transition zone. However, since these phenotypic correlations are only moderate, caution should be taken in generalizing these results for other species and other environments than those used in this study.

Both mature wood density and ring width were closely correlated to those of annual rings from the mature wood zone (Figs. 5 and 6). These results have some practical implications regarding nondestructive evaluation of wood density and growth from small samples. For example, the use of instruments such as the pilodyn would be suitable in assessing mature wood density in standing trees, as observed in white spruce (Micko et al. 1982).

CONCLUSIONS

Based on the present study, the following conclusions can be drawn:

1. For juvenile to mature wood, ring density components were significantly and negatively correlated to their respective ring width components. Thus, large ring width and earlywood width led to low ring density and earlywood density. However, latewood width was positively correlated to both ring density and latewood density.
2. Except latewood proportion, the coefficients of correlation of density and growth components with ring density tended to decrease with increasing tree age. Thus, the negative impact of ring width on ring density tends to disappear with the aging of the cambium.
3. Significant correlations between juvenile and whole tree wood characters indicated that trees having at least 12 annual rings from the pith could be used to predict to a certain extent the wood characters of these trees at older ages. However, the correlations between juvenile and mature

wood characters, although significant, range from low to moderate. Thus, using juvenile characters to predict mature wood ones could be misleading, especially for selection and breeding purposes.

4. Individual annual rings can be used to predict wood density of either mature wood or the whole tree. However, these individual rings should be sampled from the juvenile to mature wood transition zone.

ACKNOWLEDGMENTS

We thank F. Larochelle (CRBF, Université Laval) and G. Gagnon (ministère des Ressources naturelles du Québec) for helping with core sampling and tree measurements and G. Chauret (Forintek Canada Corp.) for assistance in X-ray densitometry measurements. We are also grateful to M. Villeneuve (ministère des Ressources naturelles du Québec) and M. Labarre for making accessible the provenance test and the commercial plantation, respectively. This research was made possible by a strategic research grant from the Natural Sciences and Engineering Research Council of Canada and a research grant from the ministère des Ressources naturelles du Québec. We also thank Dr. Bruce Zobel and Dr. Robert Kellogg for their helpful comments on an earlier draft of the manuscript and Ms. Pamela Cheers (Laurentian Forestry Center, Canadian Forest Service) for the editorial revision of the manuscript.

REFERENCES

- ABDEL-GADIR, A. Y., R. L. KRAHMER, AND M. D. McKIMMY. 1993. Relationships between intra-ring variables in mature Douglas-fir trees from provenance plantations. *Wood Fiber Sci.* 25(2):182-191.
- BEAULIEU, J., AND A. CORRIVEAU. 1985. Variabilité de la densité du bois et de la production des provenances d'épinette blanche, 20 ans après plantation. *Can. J. For. Res.* 15(5):833-838.
- , ———, AND G. DAOUST. 1989. Phenotypic stability and delineation of black spruce breeding zones in Quebec. *For. Can. Serv. Inf. Rep. LAU-X-85E*. Laurentian For. Cent., Sainte-Foy, QC. 39 pp.
- BENDTSEN, B. A. 1978. Properties of wood from improved and intensively managed trees. *Forest Prod. J.* 28(10): 61-72.

- BLOUIN, D., J. BEAULIEU, G. DAOUST, AND J. POLIQUIN. 1994. Wood quality of Norway spruce grown in plantations in Quebec. *Wood Fiber Sci.* 26(3):342–353.
- BOYLE, T. J., J. J. BALATINECZ, AND P. M. MCCAW. 1987. Genetic control of some wood properties of black spruce. 21st Can. Tree Improvement Association. Truro, Nova Scotia, Canada. P. 198.
- CORRIVEAU, A., J. BEAULIEU, AND F. MOTHE. 1987. Wood density of natural white spruce populations in Quebec. *Can. J. For. Res.* 17(7):675–682.
- , ———, J. POLIQUIN, AND J. DOUCET. 1990. Densité et largeur des cernes des populations d'épinettes blanches de la région forestière des Grands Lacs et du Saint-Laurent. *Can. J. For. Res.* 20(2):121–129.
- , ———, AND G. DAOUST. 1991. Heritability and genetic correlations of wood characters of Upper Ottawa Valley white spruce populations grown in Quebec. *For. Chron.* 67(6):698–705.
- HALL, J. P. 1984. The relationship between wood density and growth rate and the implications for the selection of black spruce. Newfoundland For. Res. Cent. Inf. Rep. N-X-224. Can. For. Serv., St-John's Newfoundland, Canada. 22 pp.
- KEITH, C. T. 1961. Characteristics of annual rings in relation to wood quality for white spruce. *Forest Prod. J.* 11(3):122–126.
- , AND R. M. KELLOGG. 1986. Wood quality considerations in tree improvement programs. Proc. Workshop held in Quebec City, 19 August 1995. Special publication SP-513-E Forintek Canada Corp., Ottawa, Canada. Pp. 21–25.
- KELLER, R., AND M. THOBY. 1977. Liaisons entre l'état juvénile et l'état adulte pour quelques caractères technologiques et auxométriques chez le Douglas (*Pseudotsuga menziesii*). *Ann. Sci. For.* 34(3):175–203.
- KELLOGG, R. M. 1989. Second growth Douglas-fir: Its management and conversion for value. Special Publication SP-32, Forintek Canada Corp., Vancouver, BC, Canada. 173 pp.
- KOUBAA, A., N. ISABEL, S. Y. ZHANG, J. BEAULIEU, M. BERNIER-CARDOL, AND J. BOUSQUET. 1999. Transition from juvenile to mature wood in *Picea mariana* (Mill.) B.S.P. *Can. J. For. Res.* (Accepted).
- LAMBETH, C. C. 1980. Juvenile-mature correlations in *Pinaceae* and implications for early selection. *For. Sci.* 26(4):571–580.
- MAGNUSSEN, S., AND C. T. KEITH. 1990. Genetic improvement of volume and wood properties and volume of jack pine: Selection strategies. *For. Chron.* 66(3):281–286.
- MCKEAND, S. E. 1988. Optimum age for family selection for growth in genetic tests of loblolly pine. *For. Sci.* 34(2):400–411.
- MICKO, M. M., E. I. C. WANG, F. W. TAYLOR, AND A. D. YANCHUK. 1982. Determination of wood specific gravity in standing white spruce using a pilodyn tester. *For. Chron.* 58(4):178–180.
- NEPVEU, P., AND Y. BIROT. 1979. Les corrélations phénologiques juvénile-adulte pour la densité du bois et de la vigueur chez l'épicéa. *Ann. Sci. For.* 36(2):125–149.
- NETER, J., W. WASSERMAN, AND M. H. KUNTER. 1985. Applied linear statistical models: Regression, analysis of variance, and experimental designs, 2nd ed. Richard D. Irwin Inc., Homewood, IL. 1127 pp.
- OLESEN, P. O. 1976. The interrelation between basic density and ring width of Norway spruce. *Forst. Forsogs-vaes. Dan.* 34(4):339–359.
- PANSHIN, A. J., AND C. DE ZEEUW. 1980. Textbook of wood technology, 4th ed. McGraw-Hill Book Co., New York, NY. 722 pp.
- RISI, J., AND E. ZELLER. 1960. Specific gravity of the wood of black spruce (*Picea mariana* (Mill.) B.S.P.) grown in a *Hylocomium-Cornus* site type. Laval Univ. For. Res. Found., Québec, Canada. 70 pp.
- ROZENBERG, P., AND C. CAHALAN. 1997. Spruce and wood quality: Genetic aspects (a review). *Silvae Genet.* 46(5):270–279.
- SAS INSTITUTE INC. 1988a. SAS user's guide: Basic, version 6.03 edition. SAS Institute Inc., Cary, NC.
- . 1988b. SAS user's guide: Statistics, version 6.03 edition. SAS Institute Inc., Cary, NC.
- STRAUSS, S. H., R. LANDE, AND G. NAMKOONG. 1992. Limitations of molecular-marker-aided selection in forest tree breeding. *Can. J. For. Res.* 22(7):1050–1061.
- VARGAS-HERNANDEZ, J., AND W. T. ADAMS. 1992. Age-age correlations and early selection for wood density in young coastal Douglas-fir. *For. Sci.* 38(2):467–478.
- ZHANG, S. Y. 1994. Mechanical properties in relation to specific gravity in 342 Chinese woods. *Wood Fiber Sci.* 26(4):512–526.
- . 1995. Effect of growth rate on wood specific gravity and selected mechanical properties in individual species from distinct wood categories. *Wood Sci. Technol.* 29(6):451–465.
- . 1998. Effect of age on the variation, correlations and inheritance of selected wood characteristics in black spruce (*Picea mariana*). *Wood Sci. Technol.* 32(3):197–204.
- , AND E. K. MORGENSTERN. 1996. Genetic variation and inheritance of wood density in black spruce (*Picea mariana*) and its relationship with growth: Implications for tree breeding. *Wood Sci. Technol.* 30(1):63–72.
- , D. SIMPSON, AND E. K. MORGENSTERN. 1996. Variation in the relationship of wood density with growth in 40 black spruce (*Picea mariana*) families grown in New Brunswick. *Wood Fiber Sci.* 28(1):91–99.
- ZHOU, H., AND I. SMITH. 1991. Factors influencing bending properties of white spruce lumber. *Wood Fiber Sci.* 23(4):483–500.
- ZOBEL, B. J., AND J. B. JETT. 1995. Genetics of wood production. Springer-Verlag, Berlin, Germany. 337 pp.
- , AND J. R. SPRAGUE. 1998. Juvenile wood in forest trees. Springer-Verlag, Berlin, Germany. 300 pp.
- , AND J. P. VAN BUITENEN. 1989. Wood variation: Its causes and control. Springer-Verlag, Berlin, Germany. 363 pp.