

# BEHAVIOR OF NAILED CONNECTIONS AT ELEVATED TEMPERATURES

*Suzanne M. Peyer*<sup>1</sup>

Research Assistant  
University of Wisconsin-Madison

and

*Steven M. Cramer*

Professor  
Department of Civil and Environmental Engineering  
University of Wisconsin-Madison  
Madison, WI 53706

(Received August 1998)

## ABSTRACT

The lateral resistance of plywood-to-wood nailed joints with interlayer gaps was measured at four temperatures of ambient (30°C), 120°C, 200°C, and 265°C in an exploratory test program. As temperature increased from ambient, strength decreased by 13%, 15%, and 26%, respectively, and slip modulus decreased by 47%, 61%, and 54%, respectively. The largest incremental percent decreases in strength and slip modulus occurred at the lowest temperature increment, between ambient and 120°C. Slip modulus was more negatively affected by temperature than strength. Failure mode IV (two-point nail yield) occurred on nailed joints tested at ambient, 120°C, and 200°C, but shifted to failure mode IIIs (one-point nail yield in main member) at 265°C. The shift in failure mode occurred because nonuniform temperatures throughout the joint differentially changed the embedding strength of the wood members. The yield theory predicted failure mode IV for nailed joints tested at ambient, but overestimated the strength of the joint by 40%. The results of this research support recent findings reported by Noren (1996).

**Keywords:** Nails, fire, high temperature, lateral resistance, strength, slip modulus, failure mode, yield theory.

## INTRODUCTION

For several decades, the lateral resistances of nailed joints have been tested and theoretical models have been developed to describe the failure, strength, and slip modulus of joints. Despite the amount of research conducted on the lateral resistances of nailed joints, most studies have focussed on testing and modeling nailed joints at ambient temperature (Kuenzi 1955; Foschi 1974; Foschi and Bonac 1977; Larsen 1977; Aune and Patton-

Mallory 1986a, b; Pellicane 1991, 1993; Pellicane et al. 1991; Sa Ribeiro and Pellicane 1992) and until recently, relatively few studies had been done on joints tested at elevated temperatures. The motivation for testing nailed joints at elevated temperatures has resulted from some of the drawbacks of current fire endurance testing. Fire endurance tests for nailed wood structures (ASTM 1997a) typically involve exposing a full-scale assembly to a fire and recording the time until the assembly collapses. Such tests provide qualification information on the structural integrity of these assemblies, but often the assemblies are too complex to fully understand or model their be-

<sup>1</sup> Current Address: Wood Materials and Engineering Laboratory, Washington State University, Pullman, WA 99164-1806.

havior. To understand and predict failure of assemblies at elevated temperatures, researchers (Fuller 1990; Fuller et al. 1992; Noren 1996) have begun to focus on testing subcomponents of the assemblies, such as nailed joints. These tests are similar to those that have been conducted at ambient temperatures.

Our main objective was to demonstrate how temperatures in a controlled thermal environment affect the failure mode, strength, and slip modulus of a plywood-to-wood nailed joint subjected to lateral loading. We designed a test device as close as feasibly possible to the devices (Liu and Soltis 1984; Lau and George 1987) that have been suggested as replacements to the standard (ASTM 1997b) for testing nailed joints. We exposed nailed joints (one configuration and one nail size) to four temperatures of ambient (30°C), 120°C, 200°C, and 265°C with five load tests at each condition. These temperatures were chosen to correspond in a general way with temperatures that might occur within joints in a protected assembly, rather than a situation where combustion, charring, and temperature rise are unabated. The test program was not designed to measure or estimate the actual temperatures that occur within connections in a standardized-protected-assembly fire test. This test program was exploratory and intended to reveal general trends. We did not attempt to statistically define data distributions of load-displacement. A secondary objective was to gain an initial understanding of the mechanics of the connection where temperature and moisture contents within the connection were not uniform. For ambient temperature only, we compared the resulting failure mode, strength, and load-displacement curve (including slip modulus) to that predicted by the yield theory. Finally, we discuss some issues of applying the yield theory to nailed joints tested at elevated temperatures. Our study parallels Noren's (1996) work, and we compared and contrasted our results with his results.

#### METHODS

The connection configuration consisted of two pieces of aspen plywood nailed to a south-

ern pine 2-by-4 (38-mm by 89-mm) (Fig. 1). The 2-by-4 members were cut from four clear boards, 1.2 m. (4 ft) in length. The plywood members were cut from one 16-mm ( $\frac{5}{8}$ -in.)-thick sheet (5 ply, type CD) such that the orientation of the face grain was perpendicular to the direction of loading. All wood members were conditioned at 23°C and 50% relative humidity for a least five days before the specimens were assembled. When we assembled and tested the specimens, the moisture content of the 2-by-4 members ranged from 11% to 15%. One 6d common nail connected each plywood member to the 2-by-4. For each specimen, the two nails were vertically offset by 6 mm ( $\frac{1}{4}$  in.). We used a hand press to drive the nails into the wood such that the nailheads were flush with the plywood. To prevent interlayer friction (Liu and Soltis 1984; Lau and George 1987) from developing between the plywood and 2-by-4, we situated two 1.6-mm shims adjacent to each nail while pressing the nails into the wood. Before testing the specimens, we removed the shims. This interlayer gap was used to produce test results independent of interlayer friction that may or may not develop in connections in service.

We modified the test device from the standard (ASTM 1977b) for testing two member nailed joints, and the devices that Liu and Soltis (1984) and Lau and George (1987) recommended replace the standard. The test device that we designed for a three-member specimen allowed a concentric load to be applied, which was more suitable for testing a nailed joint within a small oven with vertically aligned holes to the outside. We also eliminated the rollers that had been used (Liu and Soltis 1984; Lau and George 1987) to support the main member, because the rollers would expand and potentially bind at elevated temperatures. Our test device (Fig. 2) had lateral brackets that fully supported the plywood and adjustable angles that clamped down on top of the plywood. A stirrup surrounded the 2-by-4 and was bolted to a cylinder that was attached to a 22.2-kN (5,000-lb) load cell outside of the oven (Fig. 3). A tensile load applied to the

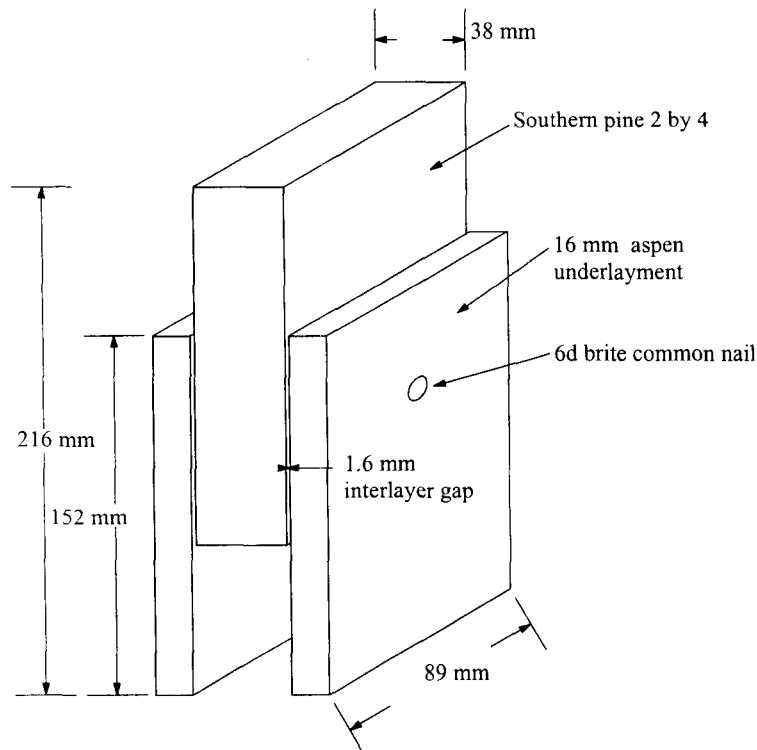


FIG. 1. Test specimen.

stirrup lifted the 2-by-4 at a displacement rate of 2.5 mm/min while the adjustable angles held the plywood stationary. As load was applied, a rod resting on a bracket attached to the 2-by-4 extended up out of the oven and attached to the core of an LVDT that was mounted to the top exterior of the oven (Fig. 3). After each test, we disassembled each specimen and determined the moisture content (ASTM 1997c) of the 2-by-4. Five joints were tested at each temperature of ambient (30°C), 120°C, 200°C, and 265°C. All temperatures were below the level that would char the wood or cause combustion. For the tests conducted at elevated temperatures, we preheated the oven to the designated testing temperature, secured the specimen in the test device, and inserted thermocouples (Type T) into 1.6-mm holes drilled in the plywood and 2-by-4 (Fig. 4). We sealed the thermocouple holes with tape, heated the specimen for an additional 60

to 80 min, and then tested the joint. The total joint displacement was 25 mm and the duration of each load-displacement test was 10 min.

For ambient temperature only, we used the yield theory to predict the ultimate strength and failure mode (NDS 1997) of the joint. Technically, the yield theory is used to predict the yield strength of a nailed joint. Here we assumed the yield strength to be equivalent to the ultimate strength, as Aune and Patton-Mallory (1986a) suggested was appropriate. We derived all yield theory equations, because they were not provided for a joint with both an interlayer gap and wood members with unequal embedding strengths (Peyer 1995). The resulting equations included expressions for the ultimate strength and required thickness of the plywood and 2-by-4 that produce a given failure mode.

For exposure temperatures of ambient,

120°C, and 200°C, we observed failure mode IV, and at 265°C we observed failure mode IIIs. Failure mode IV (two-point nail yield) (Fig. 5) occurs when Eqs. 1 and 2 are satisfied.

$$t_1 \geq 2\sqrt{\frac{M_y}{\beta f_c}} + \frac{\sqrt{\Delta^2 + \frac{4M_y}{f_c} + \frac{4M_y}{\beta f_c}} - \Delta}{\beta + 1} \quad (1)$$

$$t_2 \geq 2\sqrt{\frac{M_y}{f_c}} + \frac{\beta \sqrt{\Delta^2 + \frac{4M_y}{f_c} + \frac{4M_y}{\beta f_c}} - \beta \Delta}{\beta + 1} \quad (2)$$

The ultimate strength ( $F_u$ ) for two-point nail yield can then be computed using Eq. (3).

$$F_u = \frac{2\sqrt{\beta f_c (\beta f_c \Delta^2 + 4M_y)} - 2\beta f_c \Delta}{\beta + 1} \quad (3)$$

The parameters in Eqs. (1), (2), and (3) are as follows:

$t_1$  = plywood (side member) thickness,

$t_2$  = 2-by-4 (main member) thickness,

$M_y$  = yield moment of nail,

$f_c$  = effective embedding strength of the 2-by-4,

$\beta$  = plywood embedding strength divided by 2-by-4 embedding strength, and

$\Delta$  = dimension of the interlayer gap.

Failure mode IIIs (one-point nail yield in main member) (Fig. 5) occurs when Eqs. (4) and (5) are satisfied, and the ultimate strength can then be computed using Eq. (6).

$$2\sqrt{\frac{M_y}{\beta f_c}} - \frac{\sqrt{\Delta^2 + \frac{4M_y}{f_c} + \frac{4M_y}{\beta f_c}} + \Delta}{\beta + 1} < t_1 < 2\sqrt{\frac{M_y}{\beta f_c}} + \frac{\sqrt{\Delta^2 + \frac{4M_y}{f_c} + \frac{4M_y}{\beta f_c}} - \Delta}{\beta + 1} \quad (4)$$

$$t_1 > \frac{\sqrt{\Delta^2 + \frac{4M_y}{f_c} + \frac{4M_y}{\beta f_c}} - \Delta}{\beta + 1} \quad (5)$$

$$F_u = \left[ 2f_c \left( \frac{4\beta M_y (2\beta + 1)}{f_c} + 2\beta^2 (\beta t_1^2 + 2\Delta^2 + t_1^2 + 2t_1 \Delta) \right)^{1/2} - 2\beta \Delta - \beta t_1 \right] / (\beta + 1) \quad (6)$$

Parameters used in Eqs. (4), (5), and (6) are the same as those defined for Eqs. (1), (2), and (3). Refer to Peyer (1995) for derivations.

Predicting strength and failure mode of the joint using the yield theory requires inputting the embedding strength of the wood and the yield moment of the nail. To estimate the embedding strength of the 2-by-4 and plywood at ambient temperature, we conducted non-standard embedding strength tests. We cut five 25-mm-high specimens from each of two clear 1.2-m 2-by-4s and ten 25-mm-high by 89-mm-wide specimens from the 16-mm sheet of aspen plywood. We placed a 6d common nail parallel to the 38-mm dimension of the 2-by-4 and 16-mm dimension of the plywood such that the orientation corresponded with the specimens used for the lateral resistance tests. With an 89-kN testing machine, a load was applied to the nail at a displacement rate of 2.5 mm/min. The test was stopped when the nail was embedded in the wood up to the nail diameter of 2.9 mm. The maximum load was recorded and later used as the embedment strength. For each specimen, we conducted one test in the center of the specimen for a total of ten tests each for the 2-by-4 and plywood. To estimate the yield moment of the 6d nails used in the above tests, we conducted bending tests on 10 nails. The nails were supported at both ends, allowing a span of 32 mm, and a concentrated load was applied to the nails midway between the supports. The load was applied at a displacement rate of 0.51

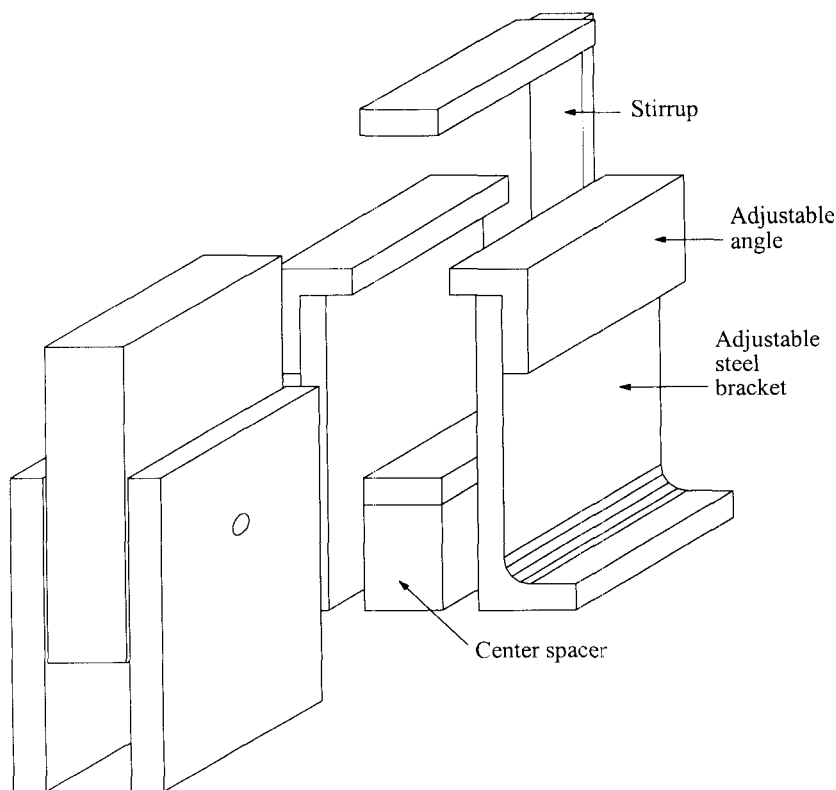


FIG. 2. Test device.

mm/min using a 534-kN testing machine until yielding occurred.

Embedding strength and nail bending tests were conducted at ambient temperature only. The scope of this research did not allow measurement of these parameters at elevated temperatures. These measurements would be needed to evaluate the yield theory at elevated temperatures as in Eqs. (3) and (6).

For structural analysis of assemblies at elevated temperature, predicting the displacement behavior of the joint is needed rather than simply the strength of the joint. We explored the derivation of a yield theory equation that would describe the entire load-displacement curve of the joint and an initial, low-load slip modulus. To derive this equation, we used the fourth-root embedding stress-deformation relationship described by Aune and Patton-Mallory (1986a, b) for a nailed joint with an interlayer gap. For sim-

plicity we assumed that the embedding strengths of the 2-by-4 and plywood were equal, and we considered only the failure mode that occurred at ambient. While we successfully derived the load-displacement equation, including the interlayer gap in the derivation, we could not resolve the equation to a usable form (Peyer 1995). The main problem was the complexity introduced by the fourth-root embedding stress-deformation equation combined with the interlayer gap. If a more simple equation could be established to describe the shank embedding behavior, replacing the fourth-root equation, then the solution of a practical yield theory load-displacement equation would be more likely.

Although we were unable to characterize the joint load-displacement measurements with the yield theory, we did analyze the data with an empirical model. The load-displacement curves were characterized by Eq. (7)

where parameters,  $k$ ,  $M_0$ , and  $M_1$  were evaluated to provide a visual best-fit to the data (see Fig. 6).

$$F = \frac{M_0}{1.5} \arctan\left(\frac{1.5d}{M_0}(k - M_1)\right) + M_1 d \quad (7)$$

In Eq. (7),

$F$  = force,

$k$  = initial slope of the load-displacement curve,

$M_1$  = slope of the load-displacement curve representing the plastic-action plateau,

$M_0$  = load axis intercept of a tangent to the load-displacement curve with slope  $M_1$ , and

$D$  = displacement.

This three-parameter equation (Eq. 7) from Shrestha et al. (1995) is modified from an equation first proposed by Foschi (1977) to characterize nailed joint load-displacement response. The Foschi equation uses the same three parameters. The modification by Shrestha et al. yields an equation that can be more readily differentiated and integrated in structural calculations.

## RESULTS

As joint displacement increased, the load increased to the ultimate strength (Fig. 6) and then tapered off as the maximum displacement of 25 mm was approached. Some friction developed between the plywood and 2-by-4, but only during the end of the test at large displacements. The LVDT operated smoothly for the ambient tests, but at elevated temperatures the core of the LVDT expanded and did not glide within the LVDT casing. We compared the ambient load-displacement curves generated by the LVDT with an internal LVDT in the load actuator. Both curves were the same; therefore we assumed that the load-displacement curves at elevated temperatures were adequately described by using the displacement of the cross-head from the testing machine.

The average maximum strength of the joints decreased as the temperature increased (Fig. 7). Figure 7 is a box plot of the data showing the median surrounded by a box sized to include the quartile of data above and below the median. The lines extending above and below the box indicate the range of the extreme data values. The average slip modulus of the joints, as characterized by " $k$ " in Eq. (7), generally decreased as temperature increased, but increased slightly between exposures of 200°C and 265°C (Fig. 8). The box plot in Fig. 8 displays the observed data in a format similar to Fig. 7. The average measured parameters corresponding to Eq. (7) are shown in Table 1. From ambient (30°C) to 120°C, 200°C, and 265°C exposures, the percent decreases were 13%, 15%, and 26%, respectively, for strength, and 47%, 61%, and 54%, respectively, for slip modulus. The strength and slip modulus decreased by the largest percent between ambient and 120°C exposure and corresponded with the largest incremental increase in the temperatures near the nail in both the 2-by-4 and plywood (Table 1). At each temperature, the percent decrease in slip modulus was greater than the percent decrease in strength.

At 120°C, 200°C, and 265°C exposures, the wood did not char, but at 265°C, the specimens were slightly discolored. Temperatures were not uniform throughout the joint for any elevated temperature exposure nor were moisture contents of the wood materials. Any attempt to achieve uniform conditions would have resulted in very long and unrealistic exposure durations. Temperatures near the nail in the plywood were always higher than the temperatures near the nail in the 2-by-4 (Fig. 9, 10; Table 1). As the exposure temperature increased, the temperatures in the plywood increased by more than the temperatures in the 2-by-4.

At ambient (30°C), 120°C, and 200°C exposures, the nails yielded in both the plywood and the 2-by-4 and corresponded with failure mode IV (Fig. 5) in the NDS (1997). Nail yield, particularly in the plywood, was less

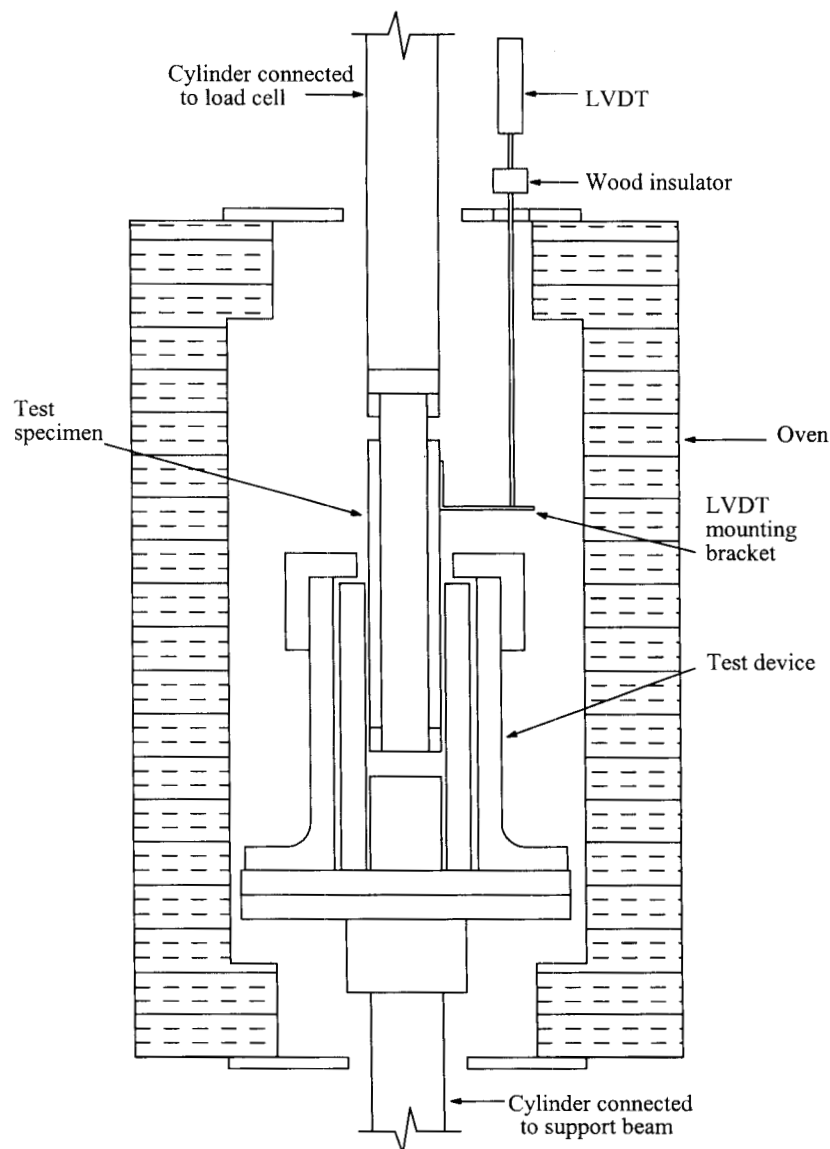


FIG. 3. Test device within oven.

dramatic as the temperature increased. At 265°C exposure, the nails yielded in the 2-by-4, but remained straight in the plywood and corresponded with failure mode IIIs (Fig. 5) in the NDS (1997). As the temperature increased, the nailheads were pulled farther into the plywood and at 265°C exposure, the plywood surrounding the nail was noticeably degraded.

At ambient, the average embedding strength of the 2-by-4 ( $f_e$ ) was 175 kN/m (1,000 lb/in.) at an average displacement of 1.8 mm (0.07 in.). The average embedding strength of the plywood was 105 kN/m (600 lb/in.) at an average displacement of 2.5 mm (0.1 in.). The resulting embedding strength ratio of the plywood to the 2-by-4 ( $\beta$ ) was 0.6. The average yield moment of the nail ( $M_y$ ) was 2.5 N-m

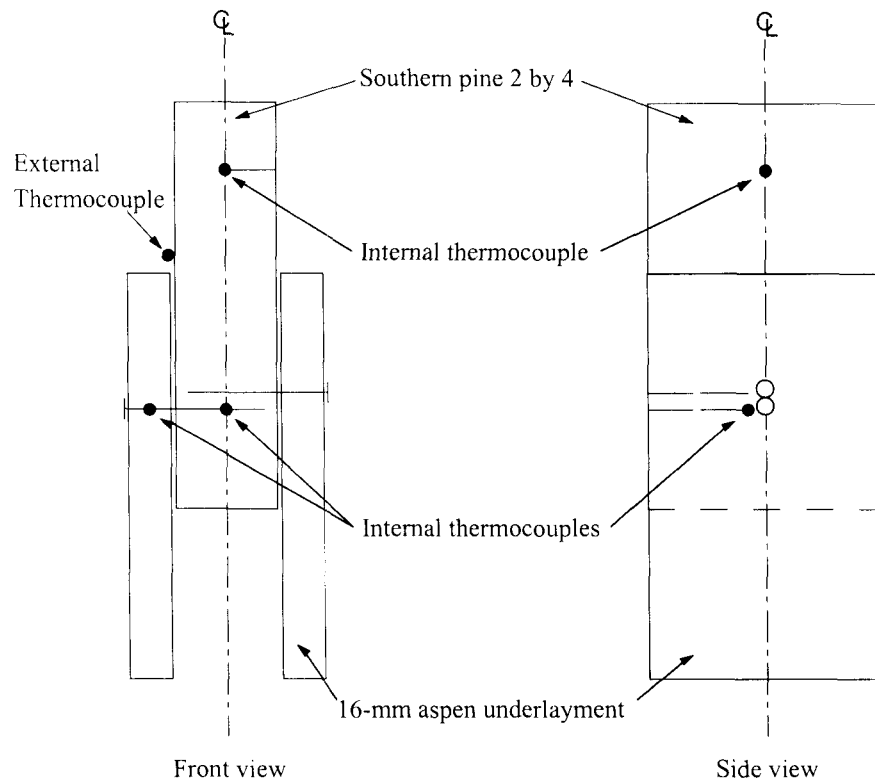


FIG. 4. Location of thermocouples in test specimen.

(22 in.-lb), roughly 30% lower than what Loferski and McLain (1990) measured for 6d nails. Nail yield occurred at an average angular deformation of 0.05 radians, consistent with what Aune and Patton-Mallory (1986b) measured for 8d, 16d, and 40d nails.

When substituted into yield theory Eqs. (1) and (2), the above values for  $f_c$ ,  $\beta$ , and  $M_v$  predicted the two-point failure mode at ambient. The actual thickness of the 2-by-4 (distance the nail penetrated the 2-by-4) was 33 mm (1.3 in.), greater than the minimum thickness of 12 mm (0.46 in.) specified by the yield theory (Eq. (2)) for nail yield within the 2-by-4. The actual thickness of the plywood was 16.0 mm (0.63 in.), very close to the minimum thickness of 16.5 mm (0.65 in.) required by the yield theory (Eq. (1)) for nail yield within the plywood. While  $f_c$ ,  $\beta$ , and  $M_v$  predicted the two-point failure mode at ambient, the yield theory (Eq. (3)) overestimated the ultimate

strength of the joint by roughly 40%. The strength predicted by the yield theory was 2.85 kN (640 lb) (Eq. (3) multiplied by two sides) compared to 1.98 kN (445 lbs) that we measured.

#### DISCUSSION

The strength and slip modulus of the nailed joints tested generally decreased as temperature increased. The largest incremental percent decrease in strength (13%) and slip modulus (47%) occurred at the lowest exposure temperature, between ambient (30°C) and 120°C, and was correlated with the largest incremental increase in temperatures near the nails in the plywood and 2-by-4. Noren (1996) also noted substantial decreases in the embedding strength of wood at 100°C. He suggests that the severe moisture loss that occurs as the temperature reaches 100°C is responsible for the



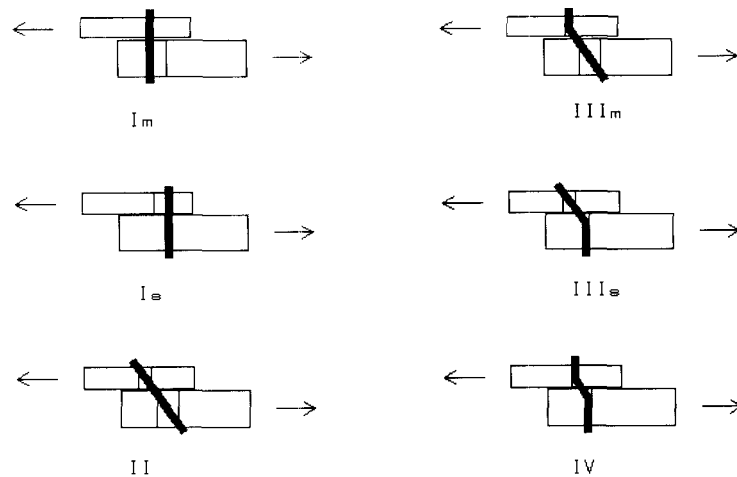


FIG. 5. Yield theory failure modes of joints.

dramatic loss of strength and slip modulus. While both the strength and slip modulus of the joints decreased as temperature increased, the slip modulus decreased by a greater percentage than the strength.

The decreases in strength and slip modulus were attributed mostly to the loss of embedding strength of the wood members. Slight reduction in the yield moment of the nails could also have occurred, but reports suggest that temperatures below 200°C have little effect on the mechanical properties of steel (Fuller 1990; Noren 1996). Knudsen and Schniewind (1975) and Gerhards (1982) illustrate the influence of temperature on various mechanical

properties of wood. In general, mechanical properties of wood decrease as wood degrades when exposed to elevated temperatures (Knudsen and Schniewind 1975; Gerhards 1982), but can also increase as the moisture content drops to 0% (Gerhards 1982). Our specimens had an initial moisture content between 11% and 15%, but we did not attempt to distinguish between the influence of moisture loss and thermal degrade on the strength and slip modulus of the joints. The net changes in strength and slip modulus were decreases, except for the slight increase in slip modulus that occurred at 265°C exposure; therefore the embedding strength of the wood

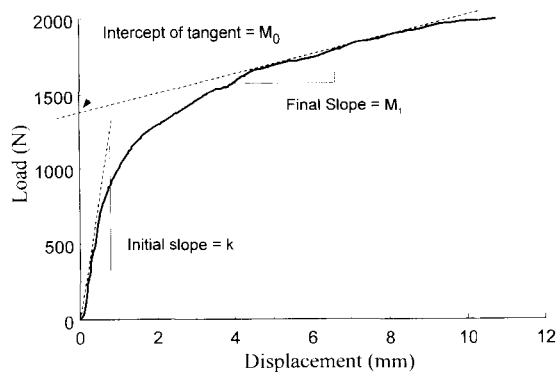


FIG. 6. Typical load-displacement curve from data and parameters ( $k$ ,  $M_0$ , and  $M_1$ ) used to fit an equation to the curve.

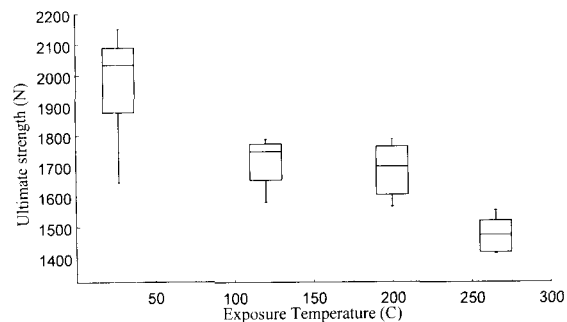


FIG. 7. Effect of temperature on strength. The median value is surrounded by the box enclosing the quartile of data above and below the median. The vertical line extending through the box indicates the full range of the data.

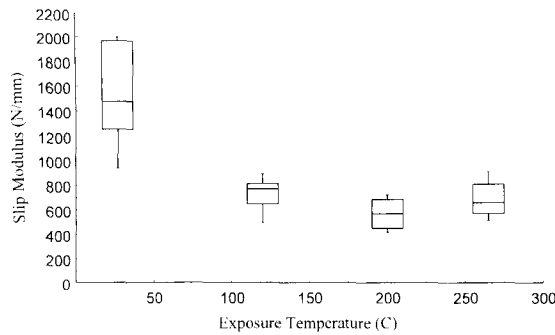


FIG. 8. Effect of temperature on slip modulus. The median value is surrounded by the box enclosing the quartile of data above and below the median. The vertical line extending through the box indicates the full range of the data.

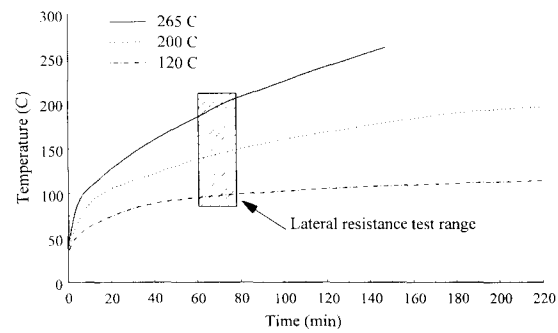


FIG. 9. Temperatures in plywood for 120°C, 200°C, and 265°C exposures.

members appeared to be more negatively affected by thermal degrade than positively affected by moisture loss. Loss of moisture, however, could have retarded the decreases in strength and slip modulus and even been responsible for the slight increase in slip modulus that occurred at the 265°C exposure. More likely this increase was an artifact of our small sample sizes or caused by inherent variations in the wood members.

Among the four exposure temperatures, we observed failure mode IV at ambient, 120°C, and 200°C and failure mode IIIs at 265°C. Temperatures were always higher in the plywood than in the 2-by-4, because the plywood was more exposed to the heat source and because the nail conducted heat from the nail head to the tip heating the plywood first (Fuller et al. 1992). Nonuniform temperatures throughout the nailed joints led to differential changes in the embedding strength of the

wood members and were responsible for the shift in failure mode that occurred.

Recently, Noren (1996) reported research that generally paralleled our study. Noren exposed various nailed joints to a fire and tested them with a constant load until failure occurred. The loads applied to the joints at elevated temperatures were different percentages of the average failure load that he measured on joints tested at ambient. Joints that he tested at loads greater than 35% of the ambient temperature failure load exhibited failure modes IIIs and IV, and below 35% of the ambient temperature failure load, mode Is occurred (see Fig. 5). While we did not test the nailed joints with constant load, the average failure loads that we measured at elevated temperatures were greater than 75% of the average failure load at ambient. The failure modes that we observed likely occurred under conditions similar to those observed by Noren. Additionally, the temperatures that Noren (1996) reported in the main and side members

TABLE 1. Measured average strength, slip modulus, and load-displacement parameters of Eq. 7 with corresponding temperatures and moisture contents. Temperature readings in the plywood and 2-by-4 were near the nail.

Exposure condition	Plywood temperature °C	2-by-4 temperature °C	% MC in 2-by-4 after test	Connection strength N	Connection initial stiffness, k N/mm	Connection plateau slope, $M_1$ , N/mm	Connection plateau slope intercept, $M_0$ , N
30°C	30	30	12	1,980	1,500	65	51
120°C	100	70	9	1,715	790	40	44
200°C	150	110	3	1,690	580	35	47
265°C	200	130	0	1,470	685	16	44

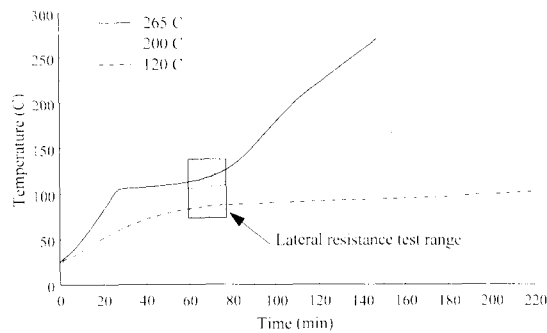


Fig. 10. Temperatures in 2 by 4 for 120°C, 200°C, and 265°C exposures.

were close to the temperatures that we recorded in our joints at about 10 min of exposure, the duration of our tests. The temperatures in the joints Noren tested were slightly lower than those we recorded, but the side members in his test joints were also thicker, making them more resistant to temperature changes.

Failure mode IV that occurred in our tests at ambient (30°C), 120°C, and 200°C demonstrated the substantial embedding strengths of the plywood and 2-by-4. The gradual loss of embedding strength in the plywood became noticeable at 120°C and 200°C and obvious at 265°C when the failure mode IIIs occurred. Similarly, Noren (1996) observed that nailed joints (series 1 and 2 in Noren's study) exhibited failure mode IV at ambient and during the first 2 min of exposure to fire, and then shifted to failure mode IIIs. Series 2 of Noren's study, in particular, had dimensions and nail size most similar to the nailed joints that we tested. Joints with thicker side members (series 3) maintained failure mode IV for up to 8 min of exposure to fire then shifted to failure mode IIIs. Failure mode Is occurred in Noren's study on nailed joints exposed to a fire for more than 10 min, which exceeded the duration of our tests. Had we tested our nailed joints for a longer period of time, we most likely would have observed failure mode Is. Although the tests conducted were not identical, our observations of connection behavior at elevated temperature are in general agreement with those of Noren (1996).

While Noren (1996) demonstrated the potential for using the yield theory to predict strength at elevated temperatures, he found that the actual and theoretical results matched well for only one out of three different relationships that modeled the reduction in embedding strength with temperature. In his evaluation, he relied on estimates of the temperature-induced reduction of embedding strength rather than actual measurements. To fully develop and apply the yield theory for elevated temperature conditions, the embedding strength of the wood and yield moment of the nail at elevated temperatures should be evaluated.

In practice, the strength and slip modulus of nailed joints under similar temperature conditions may be higher than those recorded in this study. While friction between nailed wood members is likely variable and cannot be relied upon in service, in most situations interlayer gaps of 1.6 mm would not exist either. Liu and Soltis (1984) demonstrated under room temperature conditions that slip moduli computed from test specimens with a 1.4-mm interlayer gap were in the range of 60 to 70% of those recorded with no gap.

The interlayer gap also influenced the thermal characteristics of the test joints by exposing two additional wood member surfaces and approximately 1.6 mm of nail to elevated air temperature. The gap likely accelerated the heat transfer at the member surfaces and the exposed portion of the nail. Again, such gaps may or may not occur as a structure is exposed to elevated temperatures in a distress situation. As gaps occur, Noren (1996) has shown that temperatures rise quickly with corresponding reductions in connection strength and slip modulus.

The application of connection behavior recorded in this study is intended to primarily support developments in the structural analysis of protected wood assemblies during the onset of fire. These results will be used to estimate the relative effect of temperature exposure on nailed connection performance. Use of the temperatures recorded in this study at the nail

and within the wood members would be expected to be compared to temperatures predicted with heat transfer models within a connection before the slip and strength reductions established in this study would be applied.

Certainly temperatures in assembly fire tests or in actual structure fires can well exceed those used in this study. Advancing our understanding of how wood structures deflect and resist load at the onset of standardized and real fires, when temperatures are only moderately elevated, is important since it is at the onset of a fire that safety from collapse during building evacuation or fire suppression is of most concern. Direct application of results obtained in this study to actual structures or standardized fire test assemblies must be done with caution and knowledge that test conditions match with those of the assembly both with regard to temperature exposures and connection details such as the interlayer gap. The connection tests in this study were not designed to establish the temperature conditions that exist within actual wood assemblies during fire tests or real fires.

#### CONCLUSIONS

This study demonstrated that elevated temperatures decrease the strength and slip modulus of nailed joints even at relatively low temperatures (100°C). Slip modulus was generally reduced by a greater percentage than strength. The largest incremental percent decrease in strength (13%) and slip modulus (47%) occurred between ambient (30°C) and 120°C. Failure mode IV (two-point nail yield) occurred on nailed joints tested at ambient (30°C), 120°C, and 200°C but shifted to failure mode IIIs (one-point nail yield in the main member) at 265°C. These observations confirmed similar findings by Noren. Nonuniform temperatures throughout the nailed joints led to differential changes in the embedding strength of the wood members and were responsible for the shift in failure mode that occurred. The yield theory correctly predicted failure mode IV for nailed joints tested at am-

bient, but overestimated the strength of the joint by 40% based on measured input parameters. Including an interlayer gap also led to computational difficulties when expanding the yield theory to describe the entire load-displacement curve. Considerably more development work is needed to make the yield theory a useful tool for predicting connection behavior at elevated temperature.

#### ACKNOWLEDGMENTS

The authors gratefully acknowledge partial financial support for this research from the American Forest and Paper Association. We thank Robert White, of the USDA Forest Service Forest Products Laboratory, and John Hermanson, formerly of the University of Wisconsin-Madison, for their experimental and analytical assistance, and helpful advice throughout this study. The assistance in equipment setup by John Dreger and William Lang of the Structures and Materials Testing Lab. is also appreciated.

#### REFERENCES

- AMERICAN SOCIETY FOR TESTING AND MATERIALS. ASTM E-119-95a. 1997a. Standard Test Methods for Fire Tests of Building Construction and Materials. Annual Book of ASTM Standards. Vol. 04.07:441-461. Philadelphia, PA.
- . ASTM D1761-88. 1997b. Standard Test Methods for Mechanical Fasteners in Wood. Annual Book of ASTM Standards. Vol. 04.10:269-280. Philadelphia, PA.
- . ASTM D 4442-84. 1997c. Standard Test Methods for Direct Moisture Content Measurement of Wood and Wood-Base Materials. Annual Book of ASTM Standards. Vol. 04.10:487-491. Philadelphia, PA.
- AUNE, P., AND M. PATTON-MALLORY. 1986a. Lateral load-bearing capacity of nailed joints based on the yield theory: Theoretical development. Research Paper FPL 469. USDA, Forest Serv. Forest Prod. Lab., Madison, WI.
- . 1986b. Lateral load-bearing capacity of nailed joints based on the yield theory: Experimental verification. Research Paper FPL 470. USDA, Forest Serv. Forest Prod. Lab., Madison, WI.
- FOSCHI, R. O. 1974. Load-slip characteristics of nails. Wood Science 7(1):69-76.
- . 1977. Analysis of wood diaphragms and trusses. Part II: Truss-plate connections. Can. J. Civil Eng. 4: 353-362.

- , AND T. BONAC. 1977. Load-slip characteristics for connections with common nails. *Wood Science* 9(3): 118–123.
- FULLER, J. J. 1990. Predicting the thermo-mechanical behavior of a gypsum-to-wood nailed connection. M.S. thesis, Oregon State University, Corvallis, OR.
- , R. J. LEICHTI, AND R. H. WHITE. 1992. Temperature distribution in a nailed gypsum-stud joint exposed to fire. *Fire Mater.* 16:95–99.
- GERHARDS, C. C. 1982. Effect of moisture content and temperature on the mechanical properties of wood: An analysis of immediate effects. *Wood Fiber Sci.* 14(1): 4–36.
- KNUDSEN, R. M., AND A. P. SCHNIEWIND. 1975. Performance of structural wood members exposed to fire. *Forest Prod. J.* 25(2):23–32.
- KUENZLI, E. W. 1955. Theoretical design of a nailed or bolted joint under lateral load. Rep. No. D1951. USDA, Forest Serv., Forest Prod. Lab., Madison, WI.
- LARSEN, H. J. 1977. K. W. Johansen's nail tests. *Bygningsstatistiske Meddelelser*. Vol. 48, No. 1. Aalborg, Denmark.
- LAU, P. W. C., AND P. GEORGE. 1987. Development of a load-slip test apparatus for nailed joints. *Forest Prod. J.* 37(11/12):39–44.
- LIU, J. Y., AND L. A. SOLTIS. 1984. Lateral resistance of nailed joints—A test method. *Forest Prod. J.* 34(1): 55–60.
- LOFERSKI, J. R., AND T. E. MCLAIN. 1990. Static and impact flexural properties of common wire nails. Draft submitted to *Journal of Testing and Evaluation*.
- NOREN, J. 1996. Load-bearing capacity of nailed joints exposed to fire. *Fire Mater.* 20:133–143.
- National Design Specification® for Wood Construction. 1997 Edition. American Forest and Paper Association, 164–165.
- PELLICANE, P. J. 1991. Application of the European yield model to nailed joints in southern hardwoods. *J. Testing Eval.* 19(5):385–393.
- . 1993. Plywood-solid wood nailed joints under lateral loading. *J. Mater. Civil Eng.* 5(2):226–236.
- , J. L. STONE, AND M. D. VANDERBILT. 1991. Generalized model for lateral load slip of nailed joints. *J. Mater. Civil Eng.* 3(1):60–77.
- PEYER, S. M. 1995. Lateral resistance of a plywood-to-wood nailed connection at elevated temperatures. M.S. thesis., Dept. of Civil and Environmental Engineering, Univ. of Wisconsin-Madison, WI.
- SA RIBEIRO, R. A., AND P. J. PELLICANE. 1992. Modeling load-slip behavior of nailed joints. *J. Mater. Civil Eng.* 4(4):385–398.
- SHRESTHA, D., S. CRAMER, AND R. WHITE. 1995. Simplified models for the properties of dimension lumber and metal-plate connections at elevated temperatures. *Forest Prod. J.* 45(7/8):35–42.